

# AMERICAN ENGINEERING GROUP



## “Elastomeric Seal Life Prediction” A Manufacturing Perspective

- O-ring, Gaskets, and Oil seal

Presented by

Abraham Pannikottu

*Operations Manager, AEG*

[www.engineering-group.com](http://www.engineering-group.com)

Ph: 330 375 1975



ISO 9001:2000

# **Elastomeric Seal Life Prediction A Manufacturing Perspective**

- **Topics to be Discussed**
  - **Introduction - Definitions**
  - **The AEG Approach**
  - **Three Examples**
    - Telecommunications
    - Aerospace
    - Semiconductor
  - **Future Work**

# Customer Expectations of Seal Manufacturers Today

- Expanded Temperature Ranges
- Enhanced Chemical Resistance
- Performance Vs. Material Specifications
- Statistically Capable Properties
- “Tailored” Formulas for Specific Applications
- “Zero” Defects
- “Zero” Leakage
- Predictable seal life !!!

# **The Engineering Challenge !**

- **How long can I expect your seals to last in my application?**

# Some Definition Challenges

- Useful Seal Life?
- Leakage?
- Failure?
- Application Details?

# Three Categories of Seal Failures

- **Environmental**
  - Time/Temperature dependant
  - Physical/Chemical degradation
- **Application Details**
  - Extrusion, ED, Spiraling, etc
- **Human Error**
  - Installation damage, storage conditions, handling, etc
  - Manufacturing problems with seals

# Analysis Tools for Failure Types

- **Environmental**
  - Various Predictive Models
    - Arrhenius
- **Application Details**
  - Non-linear Finite Element Modeling
- **Human Error**
  - Statistics/Probability Distributions

# AEG Approach to Seal Life Prediction

- *Precise* Definition of the Application
- Material Performance Data
- Field Failure Data
- Determination of the *Primary* Aging Phenomena
- Service History Data Gathering
- Monitoring of the Seal in Application

# AEG Approach to Seal Life Prediction

- Discuss timeframe of the analysis
- Discuss the predictive modeling options
- Determine “Seal Life” criteria
- Perform experiments as needed
- Adjust the model if time permits
- Compare with used seals if possible

# AEG Approach to Seal Life Prediction

- **Arrhenius Model Limitations**
  - Tests can be rather long duration
  - Data is recipe specific
  - physical and chemical effects are often confused
  - extrapolation must be minimized
  - Temperatures must be realistic
  - Human and Application effects cannot be handled

# Telecommunications Example

- **Application: Cellular Phone**
- **Seal Material: Conductive Elastomer**
- **Timeframe Allowed: 6 months**
- **Properties to be modeled**
  - Volume Resistivity
  - “Modified” Compression Set
- **“Failure” Criteria**
  - 0.010 ohm-cm
  - 50% Compression Set

# Telecommunications Example

- **Arrhenius Model Life Predictions**
  - Volume Resistivity: 4.5 years
  - “Modified” Compression Set: 25.5 years
- **Actual Results**
  - Volume Resistivity: 2.5 years
  - “Theoretical” Compression Set: 19 years
- **Real World “Leakage” Problem**
  - Water permeation problems after 1.5 years!

## Aerospace Example

- ***Application:*** Turbine Engine Fuel line
- ***Seal Material:*** FKM Copolymer
- **Timeframe for analysis:** 30 days!
- **Properties to be modeled**
  - “Modified” Compression Set
- **“Failure” Criteria**
  - 45% Compression Set

## Aerospace Example

- **Arrhenius Life Prediction**
  - Compression Set - 4.1 years
- **Actual Results**
  - “Theoretical” Compression Set: 3.5 years
- **Real World Problem**
  - Extrusion, nibbling, cracking after 9 months!

## Semiconductor Example

- ***Application:*** Process Chamber Cover Plate
- ***Seal Material:*** Perfluorinated Elastomer
- ***Timeframe:*** 1 year
- **Properties to be modeled**
  - Retained Sealing force(CSR)
  - Vacuum PumpDown Time
- **Failure Criteria**
  - 50% Retained Sealing Force
  - 12hr pumpdown maximum

## Semiconductor Example

- **Arrhenius Life Prediction**
  - Retained Sealing Force: 3.4 years
  - Pumpdown Time: TBD
- ***Actual Results* : TBD**
- **Real World Problems so far**
  - Possible installation damage
  - Temperature spikes outside the analysis range

## Future Work


- **Couple Finite Element Modeling with Environment Prediction Models**
- **Investigate other predictive models for inclusion into our existing materials database**
- **Continue material characterization data for engineering database ( both for FEA as well as life prediction models )**
- ***LONG TERM:* Consider the Human failure modes from a statistical point of view and incorporate into our models if possible**

## Comments/Conclusions

- Arrhenius Modeling of material properties has proven rather effective for us
- Analytical tools and novel modeling approaches continue to improve
- More intense effort is needed to merge FEM with life prediction models
- OEM's are becoming much more knowledgeable than ever before
- Volume of requests for life prediction projects is growing

## Thank you

- Product Development
- Product Manufacturing
  - FEA
- Product Design Analysis
  - Project partnership
  - Confidentiality
  - ISO 9001

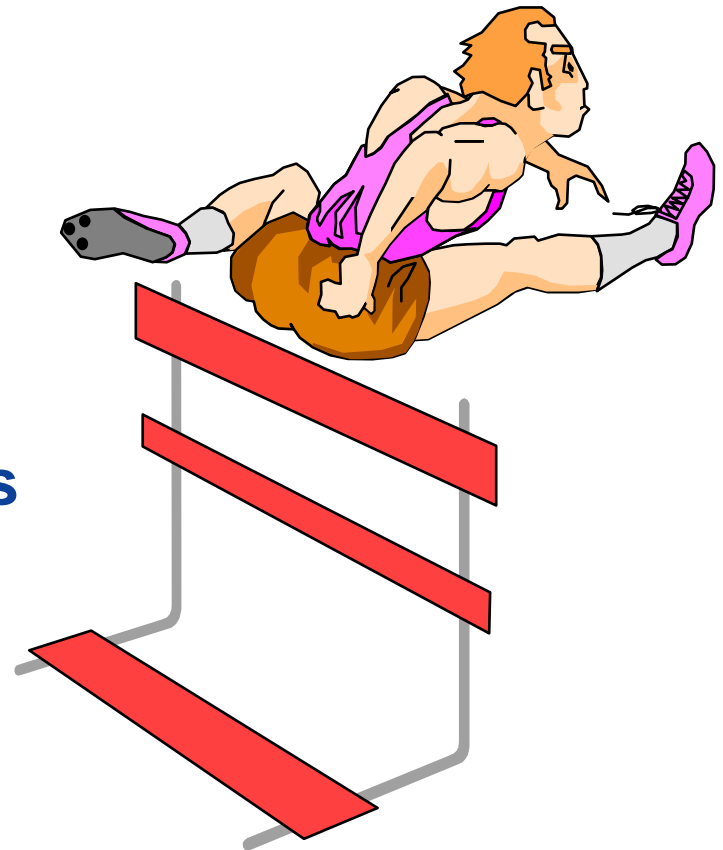

*“Progress through continuous innovation, technology and customer success”*